

2009

## One-Pot Synthesis of Anionic (Nitrogen) and Cationic (Sulfur) Codoped High-Temperature Stable, Visible Light Active, Anatase Photocatalysts

Suresh Pillai

*Technological University Dublin, suresh.pillai@tudublin.ie*


Declan McCormack

*Technological University Dublin, Declan.mccormack@tudublin.ie*

Steven Hinder

*See next page for additional authors*

Follow this and additional works at: <https://arrow.tudublin.ie/scschcpsart>

 Part of the [Chemical Engineering Commons](#), [Inorganic Chemistry Commons](#), [Materials Chemistry Commons](#), [Nanoscience and Nanotechnology Commons](#), and the [Physical Chemistry Commons](#)

### Recommended Citation

Periyat, P., McCormack, D., Hinder, S., Pillai, S.: One-Pot Synthesis of Anionic (Nitrogen) and Cationic (Sulfur) Codoped High-Temperature Stable, Visible Light Active, Anatase Photocatalysts. *J. Phys. Chem. C*, 113,(8), 2009, 3246-3253. doi: 10.21427/7dak-dj43

This Article is brought to you for free and open access by the School of Chemical and Pharmaceutical Sciences at ARROW@TU Dublin. It has been accepted for inclusion in Articles by an authorized administrator of ARROW@TU Dublin. For more information, please contact [arrow.admin@tudublin.ie](mailto:arrow.admin@tudublin.ie), [aisling.coyne@tudublin.ie](mailto:aisling.coyne@tudublin.ie).



This work is licensed under a [Creative Commons Attribution-Noncommercial-Share Alike 4.0 License](#)

---

**Authors**

Suresh Pillai, Declan McCormack, Steven Hinder, and Pradeepan Periyat

# One-Pot Synthesis of Anionic (Nitrogen) and Cationic (Sulfur) Codoped High-Temperature Stable, Visible Light Active, Anatase Photocatalysts

Pradeepan Periyat,<sup>†,‡</sup> Declan E. McCormack,<sup>\*,‡</sup> Steven J. Hinder,<sup>§</sup> and Suresh C. Pillai<sup>\*,†</sup>

Centre for Research in Engineering Surface Technology (CREST), FOCAS Institute, Dublin Institute of Technology, Camden Row, Dublin 8, Ireland, School of Chemical and Pharmaceutical Sciences, Dublin Institute of Technology, Kevin Street, Dublin 8, Ireland, and The Surface Analysis Laboratory, School of Engineering, University of Surrey, Guildford, Surrey GU2 7XH, U.K.

Received: September 23, 2008; Revised Manuscript Received: December 09, 2008

An efficient and straightforward method for the preparation of nitrogen and sulfur (N, S) codoped high-temperature stable, visible light active, anatase titania is reported. For the first time simultaneous nitrogen and sulfur doping was achieved using a single source, ammonium sulfate [(NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub>], as the modification agent of the titanium isopropoxide (TTIP) precursor. A stoichiometric modification of 1:8 TTIP:(NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub> composition (TNS8) was found to be the most effective in extending the stability of anatase to higher temperatures. This particular modification resulted in 100% anatase at 850 °C and 41% anatase at 900 °C, whereas the control titania contained only 12% anatase at 700 °C and completely transformed to rutile at 800 °C. Codoped (N, S) titania was investigated by a range of characterization techniques including XRD, Raman spectroscopy, XPS, and FTIR. XPS indicated the existence of nitrogen as an anion dopant and sulfur as a cation dopant within the TiO<sub>2</sub> lattice. The UV/visible and visible light photocatalytic studies were carried out using the rhodamine 6G dye as a model system. The visible light photocatalytic activity of the TNS8 sample calcined at 850 °C was double that of Degussa P25, and the rate constant calculated by pseudo-first-order kinetics was 0.019 min<sup>-1</sup> for the TNS8 sample and 0.008 min<sup>-1</sup> for Degussa P25. This higher photocatalytic activity was attributable to a combination of improved anatase phase stability, higher surface area, and codoped (N, S) titania lattice. Moreover, this codoped (N, S) sample also exhibits excellent photocatalytic activity under UV/visible light.

## 1. Introduction

Nanocrystalline titania is considered to be an eco-friendly material and has found applications in various fields such as photovoltaics, photocatalysis, self-cleaning coatings, and nano-chromic display devices.<sup>1–5</sup> Among the three forms of titania (anatase, rutile, and brookite), anatase usually exhibits the highest photocatalytic activity. The higher adsorption affinity toward organic compounds, along with the lower electron–hole recombination rate of anatase, phase makes it a superior photocatalyst.<sup>6,7</sup> The anatase phase is irreversibly converted to the less reactive rutile phase at 500–600 °C under normal conditions,<sup>2,8–10</sup> which limits its suitability for high-temperature applications. Many proposed innovative and commercial applications for photocatalytically active stable titania-coated materials such as bathroom tiles, sanitary wares, and self-cleaning glass for the control of organic contaminants require high processing temperatures and hence high-temperature stability.<sup>2,11,12</sup> High consumer demand is projected for these materials. To date most of the work reported to improve the thermal stability of anatase titania utilizes metal ion doping.<sup>13–15</sup> This method, which involves the addition of inorganic oxides (e.g., Al<sub>2</sub>O<sub>3</sub>, CeO<sub>2</sub>) to generate metal ions at higher temperatures, has successfully been used to control the anatase-to-rutile

transformation temperature as well as improve the photocatalytic activity of titania. However, the drawback of this method is the generation of secondary impurity phases (e.g., Al<sub>2</sub>TiO<sub>5</sub>, CeTi<sub>4</sub>O<sub>24</sub>, and Ce<sub>2</sub>Ti<sub>2</sub>O<sub>7</sub>) which affects phase purity and thus reduces the photocatalytic activity of titania.<sup>16</sup>

Chemical modification of a precursor is considered a superior method to the conventional method of metal ion doping, since it eliminates the secondary impurity phase formation. Sulfate impregnation of TiO<sub>2</sub> has recently been reported to improve the photocatalytic activity of titania.<sup>17–19</sup> For example, Colon et al. reported using this methodology to improve the phase stability of anatase up to 700 °C. They also noted the higher photocatalytic activity for the impregnated sample compared to the unmodified one. However, these materials converted to rutile phase at 800 °C, and subsequently the photocatalytic activity was also reduced.<sup>18</sup> The (NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub> impregnation on TiO<sub>2</sub> reported by Ortiz-Islas et al. showed brookite and mascagnite phase as an impurity.<sup>20</sup> Furthermore the complete phase transformation to rutile occurred in the range 650–50 °C. The effect of the SO<sub>4</sub><sup>2-</sup> and Cl<sup>-</sup> ions on the formation of anatase by the low-temperature, microemulsion modified hydrothermal method has also been reported.<sup>21</sup> Bokhimi et al. reported a comparative study of two different Cu precursors (CuCl<sub>2</sub> and CuSO<sub>4</sub>) for anatase stabilization, and the CuSO<sub>4</sub> addition retained 98% anatase at 800 °C.<sup>22</sup> However the stabilization explained in this study was due to the combined effect of metal ion (Cu<sup>2+</sup>) and SO<sub>4</sub><sup>2-</sup>. Moreover the secondary impurity phases bonattite and antierite were generated after annealing the sample at 400 and 800 °C, respectively. We have recently reported the chemical modification of titanium isopropoxide by using different nonmetallic chemical reagents such

\* Authors for correspondence. E-mail: suresh.pillai@dit.ie; declan.mccormack@dit.ie.

<sup>†</sup> Centre for Research in Engineering Surface Technology (CREST), FOCAS Institute, Dublin Institute of Technology.

<sup>‡</sup> School of Chemical and Pharmaceutical Sciences, Dublin Institute of Technology.

<sup>§</sup> The Surface Analysis Laboratory, School of Engineering, University of Surrey.

as urea, sulfuric acid, and trifluoroacetic acid to improve the anatase stability and the photocatalytic activity by doping with nitrogen, sulfur, and fluorine, respectively.<sup>2,9,23</sup>

This paper outlines the preparation of an N, S codoped anatase titania having high-temperature stability and visible-light photocatalytic activity by chemically modifying titanium isopropoxide precursor. The codoping (N, S) was achieved by using a single dopant precursor ammonium sulfate [(NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub>]. This effectively performs a dual role during the chemical modification process by stabilizing the anatase phase at higher temperature and serving as a source for both nitrogen and sulfur dopants to improve the photocatalytic activity of the high-temperature stabilized anatase titania. With this method the phase composition can be tuned by simply varying the molar ratio of ammonium sulfate to titania precursor. This modification has also resulted in increased temperature stability of anatase phase up to 900 °C (41% anatase), an increase in surface area, and a higher visible light photocatalytic activity than the standard Degussa P25. Recent studies using thiourea showed that either nitrogen or sulfur was doped in the titania lattice.<sup>24,28</sup> Surprisingly here we achieved combined anionic (nitrogen) and cationic (sulfur) doping in the titania lattice from the use of the single precursor ammonium sulfate [(NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub>].

## 2. Experimental Section

**2.1. Procedure.** The reagents used in this study were titanium isopropoxide (TTIP, 97%, Aldrich), ammonium sulfate [(NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub> 99%, Riedel-de Haen, Germany], and deionized water. In a typical experiment conducted to prepare a 1:1 titania precursor:ammonium sulfate precursor solution, 29.7 mL (100 mmol) titanium isopropoxide (Ti(OPr)<sub>4</sub>) was placed in 250 mL beaker. To the above solution was slowly added, 5 mL at a time with stirring, a solution of 13.2 g (100 mmol) of (NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub> dissolved in 180 mL of water. This was stirred for a further 15 min and then dried at 100 °C in an oven for 24 h. A similar procedure was adopted to synthesize 1:4 1:8, 1:10, and 1:12 samples. Samples were named as TNS1, TNS4, TNS8, TNS10, and TNS12, respectively. For TNS12 sample preparation, the ammonium sulfate did not dissolve completely in 180 mL of water but formed a highly saturated solution. This was used for further reaction with TTIP. A control sample without any ammonium sulfate was also prepared to act as a comparison. All samples were calcined at 700, 800, 850, and 900 °C. X-ray diffraction (XRD) patterns of the calcined sample were obtained with a Siemens D 500 X-ray diffractometer in the diffraction angle range 2θ = 10–70° using Cu Kα radiation. The amount of anatase in the sample was estimated using the Spurr equation (eq 1).

$$F_A = 100 - \left( \frac{1}{1 + 0.8(I_A(101)/I_R(110))} \right) 100 \quad (1)$$

where  $F_A$  is the mass fraction of anatase in the sample,  $I_A(101)$  and  $I_R(110)$  are the integrated main peak intensities of anatase and rutile, respectively.

Raman measurements were taken using an Instruments S.A. (Jobin Yvon) Labram 1B. A helium–neon laser (514 nm) was used as laser source. BET (Brunauer, Emmett and Teller) surface area and pore size measurements were carried out by nitrogen adsorption using a Quantachrome NOVA 2000e surface area analyzer. The measurements were carried out at liquid nitrogen temperature after degassing the powder samples for 2 h at 200 °C. The FTIR spectra of the sample were measured using a Spectrum GX-FTIR spectrophotometer in the range 4000–400 cm<sup>-1</sup> using 32 scans per sample. X-ray Photoelectron Spectroscopy (XPS) analysis was performed on a Thermo VG Scientific (East Grinstead, U.K.) Sigma Probe spectrometer. The instrument employs a monochromated Al Kα X-ray source ( $\hbar\nu$

**TABLE 1: Percentage of anatase and rutile present in control and modified samples at different temperatures<sup>a</sup>**

sample	temperature									
	700 °C		800 °C		850 °C		900 °C		1000 °C	
	A	R	A	R	A	R	A	R	A	R
TNS1	100	0	59	41	22	78	0	100	0	100
TNS4	100	0	96	4	76	24	9	91	0	100
TNS8	<b>100</b>	<b>0</b>	<b>100</b>	<b>0</b>	<b>100</b>	<b>0</b>	<b>41</b>	<b>59</b>	<b>0</b>	<b>100</b>
TNS10	100	0	100	0	100	0	40	60	0	100
TNS12	100	0	100	0	100	0	19	81	0	100
control	12	82	0	100	0	100	0	100	0	100

<sup>a</sup> Error ±5%.


= 1486.6 eV) which was used at 140 W. The area of analysis was approximately 500 μm diameter for each sample analyzed.

**2.2. Photocatalysis Studies.** The visible and UV/visible light photocatalytic activity was performed by the following approach. In a typical experiment 0.06 g of calcined sample was dispersed in 50 mL of rhodamine 6G solution having a concentration 5 × 10<sup>-6</sup> M. The above suspension was stirred for 30 min in the dark to obtain adsorption–desorption equilibrium to eliminate the error due to any initial adsorption effect. This was then irradiated in a Q-Sun Xenon solar simulator chamber having a wavelength range from 200 to 800 nm with an irradiation power 0.68 W/m<sup>2</sup>. A cutoff filter (λ = 420 nm) was used for the visible light photocatalysis to eliminate the UV light coming from the solar simulator. Degradation was monitored by taking 3-mL aliquots at different intervals of time. These aliquots were centrifuged for 15 min prior to absorbance measurements in order to eliminate the error due to scattering. Photocatalysis studies under UV/visible light were carried out by the same method without a filter.


## 3. Results

**3.1. Anatase Phase Stability by XRD and Raman Studies.** XRD analysis of the codoped (N, S) samples displayed higher anatase phase stability compared to the control titania prepared under identical conditions. Table 1 represents the fraction of anatase and rutile present in the codoped (N, S) and control sample at different calcination temperatures calculated using eq 1. All codoped samples show only anatase phase (100%) at 700 °C. In contrast the control sample was predominately rutile phase (88%). Even though (NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub> modification is effective in extending anatase phase stability in all instances, the effect is less in the lower molar ratio samples. The trend is clearly evident from Table 1 and Figures 1, 2, and 3. At 800 and 850 °C the TNS8 sample is 100% anatase phase, whereas the control titania was already completely converted to rutile phase at 800 °C. The TNS4 and TNS8 modification was found to be very effective in increasing the anatase phase stability (9% and 41% anatase phase, respectively, at 900 °C). The optimum level of modification is identified as TNS8. Raman spectroscopy was also applied to study the high-temperature stability of codoped titania as anatase and rutile phases have different Raman active modes.<sup>25</sup> Figure 4, spectra a and b, are respectively the Raman spectra of the TNS8 and control sample calcined at 800 °C. All the peaks present in the TNS8 sample were due to the anatase phase at 399, 513, and 639 cm<sup>-1</sup>.<sup>25,26</sup> In contrast the control sample with peaks at 230, 446, and 612 cm<sup>-1</sup> is clearly rutile phase.<sup>25,26</sup> At 900 °C (Figure 4c) the TNS8 sample shows 41% anatase (as per XRD) which is confirmed by anatase peaks at (399, 513, and 639 cm<sup>-1</sup>) along with rutile peaks. These Raman results are consistent with the XRD data.


**3.2. BET Surface Area Analysis.** The physicochemical sorption properties and pore parameters of the TNS8 and control

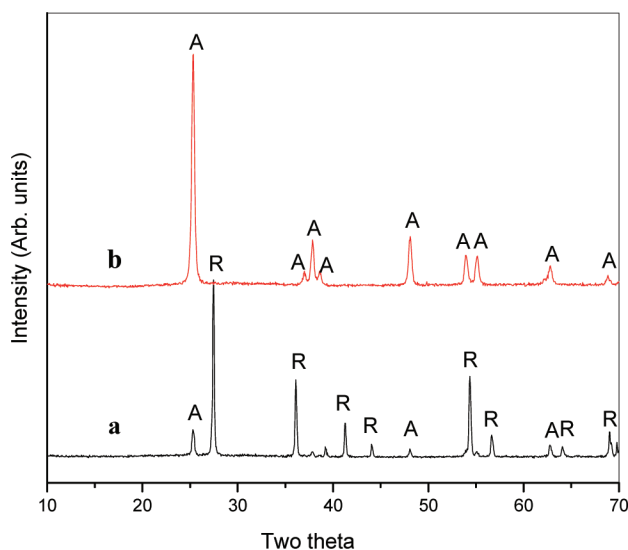


**Figure 1.** XRD spectra of the TNS8 calcined samples at 700 °C (a) and control (b).

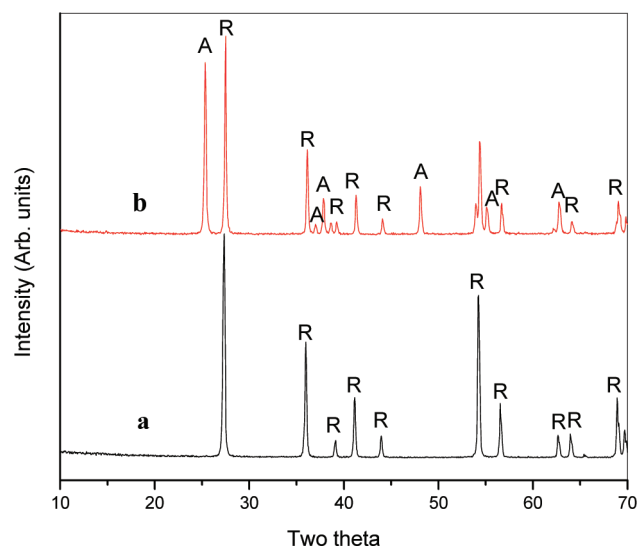

**Figure 3.** XRD spectra of the TNS8 calcined samples at 900 °C (a) and control (b).

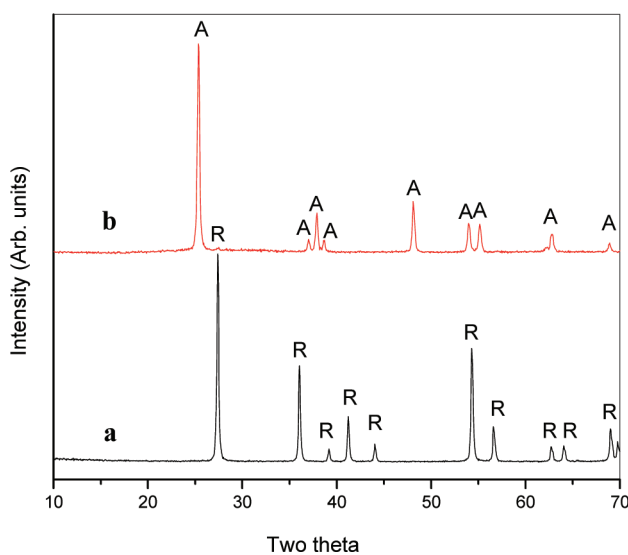

**Figure 2.** XRD spectra of the TNS8 calcined samples at 800 °C (a) and control (b).

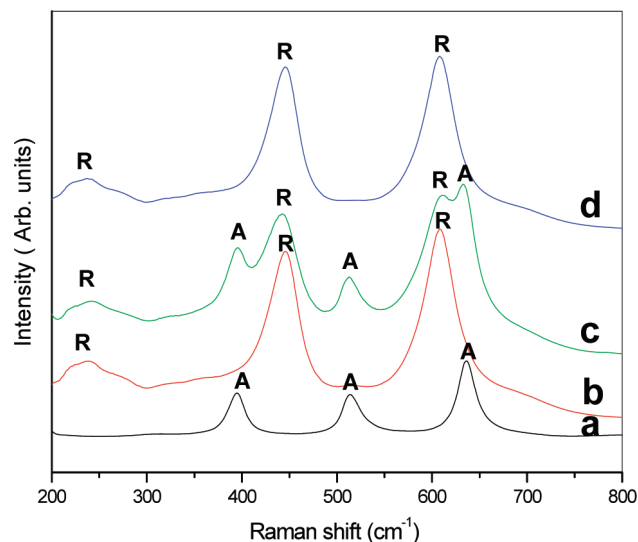

**Figure 4.** Raman spectra of (a) TNS8 at 800 °C, (b) control at 800 °C, (c) TNS8 at 900 °C, (d) control at 900 °C.

**TABLE 2: Surface area of the TNS8 and control titania at different temperatures.**

temperature (°C)	sample	BET surface area (m <sup>2</sup> /g)	pore volume (cm <sup>3</sup> /g)
700	TNS8	53.3	0.256
	control	25.6	0.160
800	TNS8	30.1	0.120
	control	1.9	0.007
900	TNS8	10.0	0.022
	control	1.0	0.00

titania samples calcined at 700, 800, and 900 °C are listed in Table 2. The nitrogen adsorption and desorption isotherm of the TNS8 and control sample shows type I isotherm (Supporting Information 1), indicating the pore size to be in the micropore range. The results indicated that the surface area and pore volume values decrease as the calcination temperature increases for both TNS8 and control sample. This is attributable to the collapse of the porous framework in both TNS8 and the control titania. This collapse was more pronounced in the control sample compared to the TNS8 sample. At 700 °C the control sample has a surface area value of 25.6 m<sup>2</sup>/g, whereas the value for the TNS8 sample is 53.6 m<sup>2</sup>/g. At 800 °C the surface areas are 1.9 and 30.1 m<sup>2</sup>/g for control and TNS8 respectively. This result indicates that the surface area decrease is more pronounced in the control compared to the codoped sample. The surface area of the TNS8 sample at 900 °C is 10 m<sup>2</sup>/g, whereas the control sample shows values only of 1 m<sup>2</sup>/g. Therefore, the modification using (NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub> was found to increase the surface area of titania significantly.

**3.3. X-ray Photoelectron Spectroscopy (XPS).** XPS measurements were carried out to investigate the N and S incorporation in the high-temperature stable anatase titania. The amount

of nitrogen and sulfur in the TNS8 samples calcined at temperatures 600, 700, 800, and 900 °C are shown in Table 3. The amount of N and S at 600 °C is significant compared to those obtained at higher temperatures. Figure 5 represents the XPS spectra of nitrogen and sulfur present in the TNS8 sample calcined at 600 and 800 °C. In Figure 5a, the binding energy peak for N-doped TNS8 sample at 600 °C is broad, extends from 398 to 405 eV, and is centered at 402 eV. This value is clearly greater than the typical binding energy (396 eV) of the Ti–N bond, suggesting that there is no Ti–N bond formation.<sup>27</sup> It was previously observed that the molecular chemisorbed

191  
192  
193  
194  
195  
196  
197  
198  
199  
200  
201  
202  
203  
204  
205  
206  
207  
208  
209  
210  
211  
212

213  
214  
215  
216  
217  
218  
219  
220  
221  
222  
223

**TABLE 3: Amount of nitrogen and sulfur present in the TNS8 sample calcined at different temperatures<sup>a</sup>**

calcination temperature (°C)	nitrogen content (atom %)	sulfur content (atom %)
600	1.5	3.5
700	0.4	0.7
800	0.2	0.3
900	0.1	0.2

<sup>a</sup> Error ± 5%.

nitrogen shows a peak at around 400 eV, and NO in the metal lattice displays a peak at 401 eV.<sup>27</sup> We suggest that the peak at 402 eV is due to the presence of both NO and chemisorbed N<sub>2</sub> species. The reason behind this suggestion is that there is a strong possibility for the formation of both species due to decomposition of NH<sub>4</sub><sup>+</sup> present in the sample when the temperature is elevated. As the temperature increases, the 402 eV peak is slightly shifted toward a lower value, suggesting that further increase in temperature led to the doping of the nitrogen in the lattice of titania by the replacement of the oxygen atom. At 800 °C this peak shows a value at 400 eV (Figure 5c), and at 900 °C it is at 399.7 eV. This peak therefore can be attributed to the 1s electron binding energy of the N atom in the O–Ti–N environment.<sup>27</sup> This O–Ti–N bond formation occurs by the replacement of the lattice oxygen by nitrogen in [TiO<sub>6</sub>]<sup>2-</sup> octahedra (basic unit of titania) and can be represented by a general formula for anionic nitrogen doping TiO<sub>2-x</sub>N<sub>x</sub> as explained in the recent reports.<sup>27</sup> Sulfur present in these samples has a peak around 169 eV which does not show any further shift as the temperature increases. This peak at 169 eV was previously explained as S<sup>6+</sup> cation present in the titania lattice.<sup>18,28,29</sup> Therefore, anionic and cationic doping was achieved in the same titania through this chemical modification method.




**3.4. Photocatalytic Study.** Photocatalytic studies were carried out using the decomposition reaction of rhodamine 6G dye in the presence of the TNS8 and control samples under UV and visible light. Pseudo-first-order degradation<sup>2</sup> rate constants, obtained by plotting the natural logarithm of the absorbance against irradiation time for the TNS8 and control samples calcined at different temperatures, are tabulated in Table 4. All the TNS8 samples calcined at different temperatures show significantly higher photocatalytic efficiency compared to the control titania prepared under identical condition. The photocatalytic activity of these codoped samples was also compared with that of the Degussa P25 photocatalyst. The highest photocatalytic activity was obtained for TNS8 sample calcined at 850 °C. This sample has higher photocatalytic activity than the Degussa P25 sample both in UV/visible and visible light. The photocatalytic activity comparison of TNS8 samples with Degussa P25 are shown in the Table 4. Figures 6 and 7 show the kinetic data and absorption spectra of rhodamine dye in the presence of TNS8 sample under UV/visible and visible light in comparison with the Degussa P25 sample. The visible light activity of TNS8 sample (rate constant 0.019 min<sup>-1</sup>) is more than twice that of the Degussa P25 sample (rate constant 0.008 min<sup>-1</sup>), whereas the control sample shows a negligible amount of visible light photocatalytic activity at this temperature (rate constant 0.001 min<sup>-1</sup>). For the control sample, the best photo-activity was shown by the sample calcined at 700 °C which has a high surface area (Table 2) compared to the same sample calcined at 800 and 900 °C.

## 4. Discussion


**4.1. Anatase Phase Stability.** The two main processes involved in the formation of a metal oxide from metal alkoxides

are hydrolysis and condensation.<sup>30</sup> The reactivity of transition metal alkoxides, particularly titanium (IV) alkoxide, particularly in relation to hydrolysis and condensation is rapid. This is due to the presence of vacant d orbitals in the transition metals which help in the co-ordination expansion.<sup>31</sup> Titanium (IV) alkoxide compounds when reacting with water increase the co-ordination number of the metal from 4 to 6, by accepting the lone pair of electrons from the oxygen of the nucleophilic ligand –O–H to form Ti(OH)<sub>z</sub>(H<sub>2</sub>O)<sub>6-z</sub>.<sup>32,21</sup> This structure undergoes dehydration and condensation to form a final precipitate of titanium hydroxide which generates crystalline titania (TiO<sub>2</sub>) on further heat treatment. In order to avoid the fast reactivity toward hydrolysis and condensation, chemical additives (complexing molecules) are often added to moderate the rate of the reaction.<sup>25,31</sup> Such control of hydrolysis and condensation reactions using urea<sup>2</sup> and trifluoroacetic acid<sup>9</sup> has led to the formation of high-temperature stable N and F doped anatase titania as previously reported by this group.

In the present study a readily available compound, ammonium sulfate, was used as a chemical modifier which is able to generate a high-temperature, stabilized N, S codoped anatase titania. The initial reaction between ammonium sulfate and titanium isopropoxide precursor led to the formation of a mixture of compounds including ammonium titanate and titanium oxysulphate (Figure 8b JCPDS file no. 81-1566). It undergoes structural changes on heat treatment due to the instability of ammonium and sulfate species present in the compound to form the high-temperature stabilized anatase titania above 600 °C. The formation of these compounds suggests that both ammonium and sulfate species are capable of inhibiting the crystallization of rutile titania at a lower temperature (below 600 °C), thereby retaining anatase titania to higher temperatures (above 600 °C). The XRD of the TNS8 sample at 100 °C shows mainly ammonium sulfate (JCPDS file no. 41-0621). This is stable up to 300 °C; however, the formation of anatase TiO<sub>2</sub> in very small quantity is also visible here which is represented by a broad peak around the 2θ value at 25.3 in Figure 8a. Further heat treatment performed for this compound at a temperature of 400 °C generated the ammonium titanate and titanium oxysulphate (Figure 8b). Above 400 °C this forms the nitrogen-doped titanium oxysulphate structure (Figure 8c, JCPDS file no. 81-1566) due to the decomposition of ammonium ions. Our previous report showed that the titanium oxysulphate decomposes at a temperature of 620 °C to produce the sulfur-doped anatase titania.<sup>23</sup> Therefore, further heat treatment of the above titanium oxysulphate causes its decomposition over a temperature above 600 °C to produce the N, S codoped anatase titania. The general reaction series can be represented by the following equations.



Therefore, the SO<sub>4</sub><sup>2-</sup> ion which is stable up to a temperature of 620 °C plays a major role in stabilizing the anatase structure along with NH<sub>4</sub><sup>+</sup> cation. IR spectroscopy reveals the role of the ammonium and sulfate species in the stabilization of the

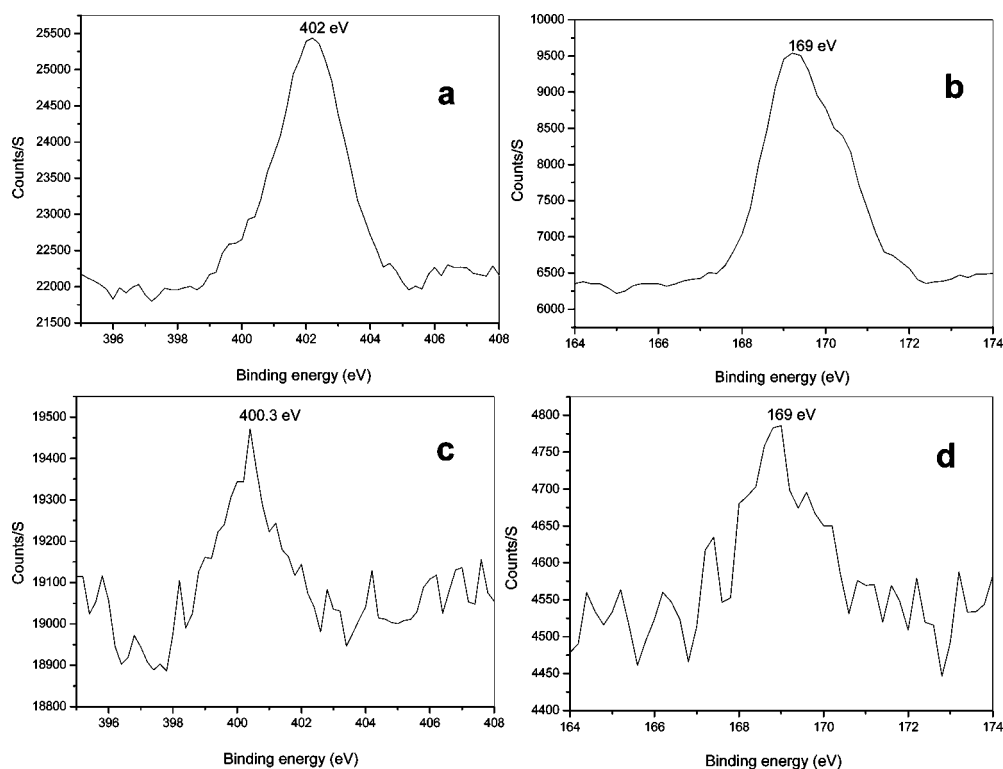

**Figure 5.** XPS spectra of (a) nitrogen and (b) sulfur at 600 °C; (c) nitrogen and (d) sulfur at 800 °C.


**TABLE 4: Rate constants of the Degussa P25, TNS8, and control titania at different temperatures**

		rate constant of the samples (units)							
		TNS8				Control			
		temperature (°C)				temperature (°C)			
light source	Degussa	700	800	850	900	700	800	850	900
UV	<b>0.281</b>	0.259	0.358	<b>0.576</b>	0.156	<b>0.101</b>	0.057	0.022	0.022
visible	<b>0.008</b>	0.014	0.016	<b>0.019</b>	0.008	<b>0.004</b>	0.002	0.002	0.001


anatase phase as well as the formation of N, S codoped anatase titania. The IR spectra of the TNS8 sample shown in Figure 9 (a, b, and c) have three main peaks at 612, 1104, and 1400 cm<sup>-1</sup>. Earlier reports showed the surface-adsorbed SO<sub>4</sub><sup>2-</sup> species has a band around 1250–1000 cm<sup>-1</sup>.<sup>33</sup> The peak around 1104 cm<sup>-1</sup> is due to the interaction of SO<sub>4</sub><sup>2-</sup> species with titania<sup>19,34</sup> which is a characteristic band of the bidentately bonded (bonded to Ti) sulfate species. The XRD pattern (Figure 8a) has the anatase peak visible at a 2θ value of 25.3° as stated earlier, but it is not sharp, and the intensity is low due to the presence of sulfate and ammonium ions present in the sample. The peak around 1400 cm<sup>-1</sup> has two possible explanations, one due to the stretching frequency of the S=O bond of free sulfate group, the other due to the deformation mode of ammonium.<sup>35</sup> However, the IR spectrum of the samples observed above 400 °C does not show this peak, which reveals that the peak is due to the ammonium ion deformation. The NH<sub>4</sub><sup>+</sup> ion begins to decompose at this temperature. The XPS study shows that at 600 °C there is 1.53 atom % (Table 3) of nitrogen in the sample which is attributed to the decomposition of the NH<sub>4</sub><sup>+</sup> cation. Above 400 °C ammonium ions are decomposed to produce N<sub>2</sub> molecules and NO species as explained in the XPS section 3.3. A further increase in temperature led to the doping of the nitrogen in the titania lattice by the replacement of the oxygen atom. This is confirmed by the XPS peak around 399.7 eV which is due to the formation of an O–Ti–N bond, suggesting that the nitrogen is doped in the lattice as an anion by the oxynitride bond formation (O–Ti–N). The interaction of sulfate ion becomes

strong above 400 °C due to the strong binding of SO<sub>4</sub><sup>2-</sup> with TiO<sub>2</sub>. This is clearly evident from the IR spectra of the samples calcined at 500 and 600 °C (Figure 9e and f) where the absorption at 1104 cm<sup>-1</sup> is split into three distinct bands (1225, 1145, and 1044 cm<sup>-1</sup>) due to the lowering of the symmetry of SO<sub>4</sub><sup>2-</sup> ion from tetrahedral (T<sub>d</sub>) to C<sub>2v</sub> point group as a result of a bidentate bond on formation of anatase titania.<sup>34</sup> The XRD of the TNS8 sample at 600 °C (Figure 8c) displays an intense peak of anatase titania at 2θ value of 25.3 which shows that the sulfate ion began to decompose at this temperature. This is confirmed by the XRD spectra of TNS8 sample at 700 °C which shows codoped (N, S) anatase titania without any extra phase (Figure 1b). This sulfate decomposition was in agreement with previous results obtained.<sup>23</sup> To confirm the effect of ammonium cation and sulfate anion on the anatase structure formation, all calcined TNS8 samples were treated with 1 M NaOH solution for 24 h. By treatment with NaOH and further washing with water, both the ammonium and sulfate ions were removed from the calcined samples. The FTIR spectra taken after NaOH treatment are shown in Figure 10. It reveals the absence of both species (ammonium and sulfate) with the spectra showing only the stretching vibration of the Ti–O–Ti bond below 1000 cm<sup>-1</sup>, along with the bands around 1600 and 3400 cm<sup>-1</sup> corresponding to the bending and stretching of the OH group of both water molecules occluded and the OH group adsorbed onto the surface of TiO<sub>2</sub>. In addition to this the XRD pattern of these NaOH-treated samples shows no other peaks except the peak for anatase titania. At lower temperatures (100 and 300 °C) TNS8 samples

335  
336  
337  
338  
339  
340  
341  
342  
343  
344  
345  
346  
347  
348  
349  
350  
351  
352  
353  
354  
355  
356  
357  
358  
359  
360  
361  
362  
363  
364  
365  
366  
367  
368  
369  
370  
371  
372  
373  
374  
375  
376  
377  
378  
379  
380  
381  
382  
383  
384  
385  
386  
387  
388  
389  
390

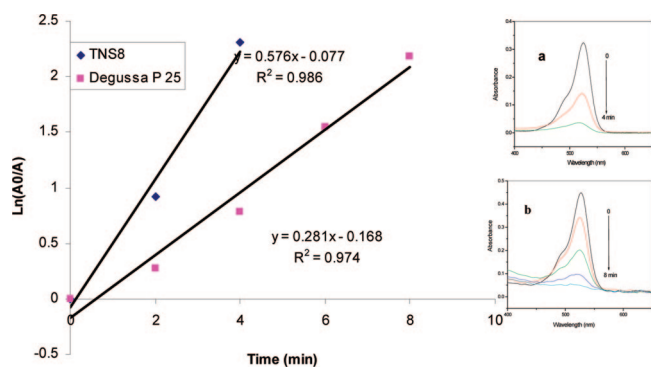


**Figure 6.** Kinetic data of the Degussa P25 and TNS8 sample calcined at 850 °C under UV/visible light photocatalysis. (Inset) Absorption spectra of rhodamine dye degradation as a function of time using (a) TNS8 (b) Degussa P 25.

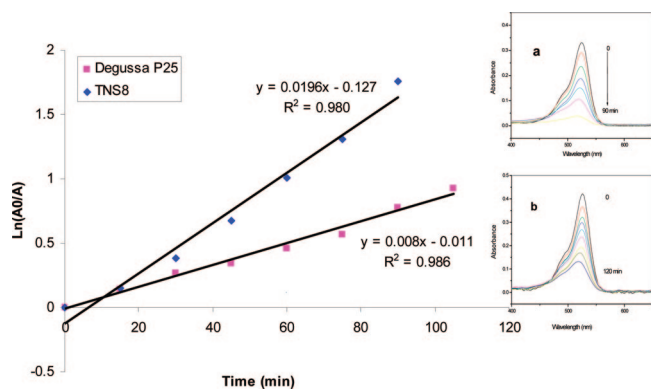

**Figure 7.** Kinetic data of the Degussa P25 and the TNS8 calcined at 850 °C under visible light photocatalysis. (Inset) Absorption spectra of rhodamine dye degradation as a function of time using (a) TNS8 (b) Degussa P25.

391 appear less crystalline, whereas the higher-temperature calcined  
 392 sample (600 °C) has well crystallized anatase titania peaks  
 393 (Supporting Information 2). This also suggests that both  
 394 ammonium and sulfate species are capable of inhibiting the  
 395 crystallization of titania at lower temperature (below 600 °C).  
 396 Therefore, the modification using ammonium sulfate reveals that  
 397 during the lower heat treatment regime the influence of  
 398 ammonium ions is predominant, while as the temperature  
 399 increases the sulfate interaction becomes more prominent. In  
 400 the present study anatase stability was achieved up to a  
 401 temperature of 900 °C.

402 **4.2. Photocatalysis.** According to literature reports organic  
 403 dyes such as methylene blue and rhodamine 6G undergo  
 404 complete structural degradation by the photocatalytic reaction  
 405 of TiO<sub>2</sub> through several intermediate steps.<sup>36–38</sup> However, the  
 406 photocatalytic activity of titania depends upon several factors,  
 407 such as phase composition (anatase and/or rutile), surface area,  
 408 crystallinity and crystallite size, absorption properties of the dyes  
 409 on the surface of TiO<sub>2</sub> used, rate of electron–hole recombina-  
 410 tion, and the number of electrons created.<sup>25</sup> Which factor  
 411 dominates the photocatalytic effect of titania is debatable.<sup>39</sup> In  
 412 this study, TNS8 samples calcined at all temperatures (700, 800,  
 413 850, and 900 °C) shows significantly higher photocatalytic  
 414 activity than the control sample (Table 4) studied under identical  
 415 conditions. The highest activity is observed for the TNS8 sample  
 416 calcined at 850 °C. The anatase phase stability of the nano-  
 417 crystalline TiO<sub>2</sub> powders at high calcination temperature and the  
 418 codoping (N, S) have a significant influence in improving the  
 419 photocatalytic activity of these TiO<sub>2</sub> samples. Direct comparison  
 420 of the crystal phase between the control and TNS8 sample shows

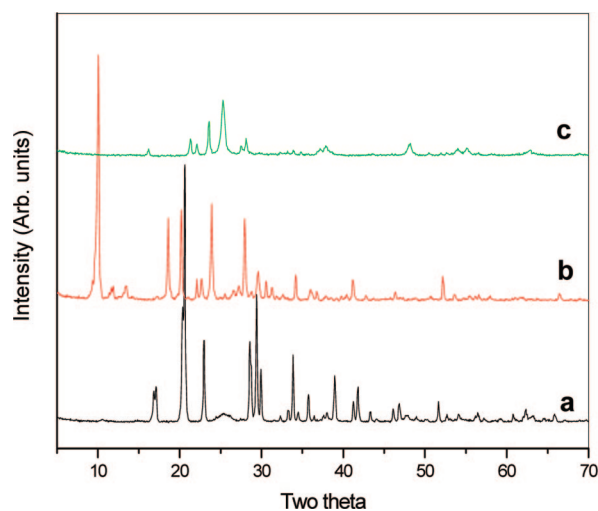


**Figure 8.** XRD spectra of the precursor samples calcined at (a) 100, (b) 400, and (c) 600 °C.


(Table 1) that the control sample is rutile at all temperatures, 421  
 whereas the TNS8 sample is anatase. Anatase titania has been 422  
 reported to be more photocatalytically active than the rutile form 423  
 because the adsorption affinity of the organic dye molecule 424  
 toward the anatase phase is stronger compared to that of 425  
 rutile.<sup>40,41</sup> The adsorption difference of the dye on TiO<sub>2</sub> phases 426  
 is mainly due to the structural difference of anatase and rutile. 427  
 Both anatase and rutile consist of tetragonal structures having 428  
 [TiO<sub>6</sub>]<sup>2-</sup> octahedra, which share edges and corners in a different 429  
 manner, while keeping the overall stoichiometry as TiO<sub>2</sub>.<sup>32</sup> 430  
 Rutile is characterized by a surface where the dissociation of 431  
 adsorbed organic molecule takes place more easily than on the 432  
 anatase.<sup>40–42</sup> These essential differences in the surface chemistry 433  
 of the two TiO<sub>2</sub> phases can explain their different photocatalytic 434  
 properties because a photocatalytic reaction mainly takes place 435  
 at the surface of the catalyst. All the codoped samples (except 436  
 the TNS8 at 900 °C (41% anatase)) show only anatase phase, 437  
 whereas the control samples show rutile phase (only at 700 °C 438  
 18% anatase phase presented) which explains the main reason 439  
 for higher photocatalytic activity shown by the codoped samples. 440

441 A further factor is the higher surface area of TNS8 samples 442  
 (Table 2). As the specific surface area of the catalyst increases, 443  
 it can adsorb a higher number of dye molecules. The TNS8 444  
 sample calcined at all temperatures shows the anatase phase 445  
 with a significantly higher surface area (more than two times 446  
 higher) compared to that of the control titania (Table 2). A 447  
 further factor to consider is the effect of codoping (N, S) which 448  
 shifts the absorption edge of the titania toward the visible light 449  
 region (Supporting Information 3) due to the synergistic effects 450  
 of nitrogen and sulfur.<sup>43,44</sup> The mixing of N<sub>2p</sub> with O<sub>2p</sub> states 451  
 will effectively lead to the band gap narrowing of titania and 452  
 the mixing of the S<sub>3p</sub> states of sulfur atoms with the valence 453  
 band increases the width of the valence band which results in 454  
 the decrease of band gap energy (Supporting Information 4, 455  
 Table 1).<sup>43,44</sup> These three factors, i.e., improvement in higher 456  
 anatase phase stability, surface area, and codoping (N, S) made 457  
 the TNS8 sample more photocatalytically active than the control 458  
 sample at all temperatures. Recent reports on the rhodamine 459  
 dye degradation mechanism using TiO<sub>2</sub> and TiO<sub>2</sub>/SiO<sub>2</sub> 460  
 composites showed that the blue shift in absorption maxima 461  
 represents the dye degradation pathway through the elimination 462  
 of the diethyl group from the dye structure.<sup>36,38</sup> In this study a 463  
 gradual decrease in absorption maxima of the dye without any 464  
 blue shift (Figures 6 and 7) was observed. Thus, it has been 465  
 concluded here that active radical species (hydroxyl and super



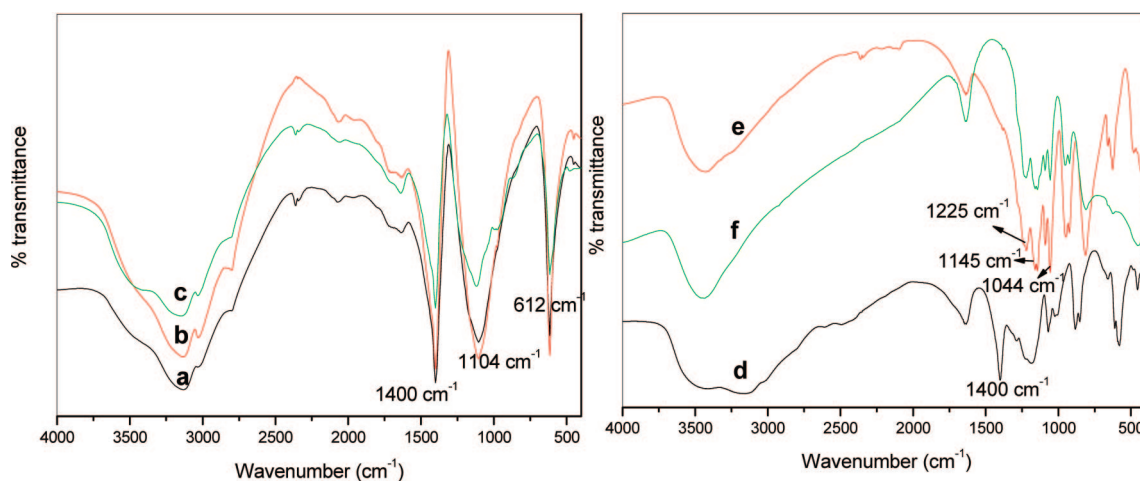

**Figure 9.** FTIR spectra of the TNS8 samples at (a) 100, (b) 200, (c) 300, (d) 400, (e) 500, and (f) 600 °C.

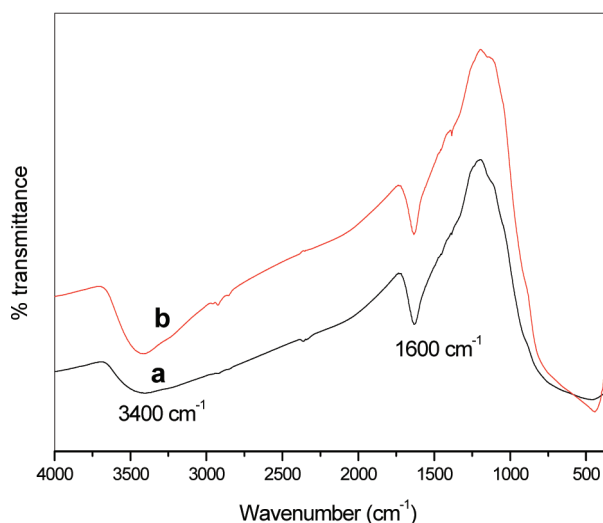

**Figure 10.** FTIR spectra of the TNS8 samples at (a) 100 and (b) 600 °C after NaOH treatment.

oxide radicals) generated during photocatalysis attack at the ring structure (chromophore) rather than attacking the diethyl amino group (auxochrome). The photocatalytic activity was also studied using another model pollutant, methylene blue, to confirm the activity of these materials on different organic pollutants. These degradation experiments showed a trend in activity similar to that of the rhodamine 6G dye degradation (Supporting Information 5).

## 5. Conclusions

Nitrogen, sulfur codoped high-temperature stable visible light active anatase titania was successfully synthesized by chemical modification of the precursor titanium isopropoxide using ammonium sulfate. These materials were characterized by various techniques such as XRD, Raman spectroscopy, FTIR, XPS, and BET surface area analysis. The phase analysis by XRD found the 1:8 TTIP:(NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub> composition (TNS8) was the most effective in extending the anatase-to-rutile phase transformation. It showed the formation of 100% anatase at 850 °C and 41% anatase at 900 °C, whereas the control titania completely transformed to rutile at 800 °C with only 12% anatase at 700 °C. XPS studies showed that nitrogen is doped as an anion and sulfur as a cation. All the doped samples showed significantly higher photocatalytic activity compared to the

control titania. The visible light photocatalytic activity comparison of the TNS8 sample calcined at higher temperature 850 °C with that of a commercial catalyst Degussa P25 showed that TNS8 has twice the activity of Degussa P25 and the rate constant calculated from first-order kinetics was 0.019 min<sup>-1</sup> for TNS8 and 0.008 min<sup>-1</sup> for Degussa P25, while the control sample showed a negligible amount of activity at this temperature. These N, S codoped samples also showed excellent photocatalytic activity in UV/visible light. The TNS8 composition calcined at 850 °C decolorized the rhodamine 6G dye within 4 min (pseudo-first-order rate constant 0.576 min<sup>-1</sup>), whereas the Degussa P25 under identical conditions decolorized the dye only after 8 min (rate constant 0.281 min<sup>-1</sup>). This higher photoactivity was explained by an improvement in anatase phase stability and higher surface area along codoping (N, S) in the titania lattice.

**Acknowledgment.** One of the authors, P.P., acknowledges R&D Strand I award 2005 from DIT. We thank Enterprise Ireland for financial support. We thank Dr. Anthony Betts and Dr. Hugh Hayden for their valuable comments.

**Supporting Information Available:** Figures giving type I isotherms of samples calcined at 800 °C, XRD patterns of the TNS8 samples at 100 and 600 °C after NaOH treatment, absorption spectra and reflectance spectra, band gaps of the N, S codoped sample calcined at different temperatures, absorption spectra and kinetic analysis of methylene blue degradation. This material is available free of charge via the Internet at <http://pubs.acs.org>.

## References and Notes

- (1) Kamat, P. V. *J. Phys. Chem. C* **2007**, *111*, 2834. Parkin, I. P.; Palgrave, R. G. *J. Mater. Chem.* **2005**, *15*, 1689.
- (2) Pillai, S. C.; Periyat, P.; George, R.; McCormack, D. E.; Seery, M. K.; Hayden, H.; Colreavy, J.; Corr, D.; Hinder, S. J. *J. Phys. Chem. C* **2007**, *111*, 1605.
- (3) Chen, X.; Mao, S. S. *Chem. Rev.* **2007**, *107*, 2891. Yamagishi, M.; Kuriki, S.; Song, P. K.; Shigesato, Y. *Thin Solid Films* **2003**, *442*, 227.
- (4) Bach, U.; Corr, D.; Lupo, D.; Pichot, F.; Ryan, M. *Adv. Mater.* **2002**, *14*, 845.
- (5) Hoffmann, M. R.; Martin, S. T.; Choi, W.; Bahnemann, D. W. *Chem. Rev.* **1995**, *95*, 69. Yang, S. W.; Gao, L. *J. Am. Ceram. Soc.* **2005**, *88*, 968.
- (6) Stafford, U.; Gray, K. A.; Kamat, P. V.; Varma, A. *Chem. Phys. Lett.* **1993**, *205*, 55.
- (7) Riegel, G.; Bolton, J. R. *J. Phys. Chem.* **1995**, *99*, 4215.
- (8) Baiju, K. V.; Periyat, P.; Wunderlich, W.; Pillai, K. P.; Mukundan, P.; Warrier, K. G. K. *J. Sol-Gel Technol.* **2007**, *43*, 283.

- 534 (9) Padmanabhan, S. C.; Pillai, S. C.; Colreavy, J.; Balakrishnan, S.;  
535 McCormack, D. E.; Perova, T. S.; Gun'ko, Y.; Hinder, S. J.; Kelly, J. M.  
536 *Chem. Mater.* **2007**, *19*, 4474.
- 537 (10) Kumar, K. N. P.; Keizer, K.; Burggraaf, A. J. *Nature* **1992**, 358,  
538 48. Czanderna, A. W.; Rao, C. N. R.; Honig, J. M. *Trans. Faraday Soc.*  
539 **1958**, *54*, 1069.
- 540 (11) Machida, M.; Norimoto, W. K.; Kimura, T. *J. Am. Ceram. Soc.*  
541 **2005**, *88*, 95.
- 542 (12) Hurum, D. C.; Agrios, A. G.; Gray, K. A. *J. Phys. Chem. B* **2003**,  
543 *107*, 10871.
- 544 (13) Periyat, P.; Baiju, K. V.; Pillai, K. P.; Mukundan, P.; Warriier,  
545 K. G. K. *Appl. Catal., A* **2008**, *349*, 13.
- 546 (14) Francico, M. Z. P.; Mastelaro, V. R. *Chem. Mater.* **2002**, *14*, 2514.
- 547 (15) Reidy, D. J.; Holmes, J. D.; Nagle, C.; Morris, M. A. *J. Mater.*  
548 *Chem.* **2005**, *15*, 3494.
- 549 (16) Periyat, P.; Baiju, K. V.; Mukundan, P.; Pillai, P. K.; Warriier,  
550 K. G. K. *J. Sol-Gel Technol.* **2007**, *43*, 299.
- 551 (17) Colon, G.; Hidalgo, M. C.; Munuera, G.; Ferino, I.; Cutrufello,  
552 M. G.; Navio, J. A. *Appl. Catal., B* **2006**, *67*, 41. Colon, G.; Espana, J. M. S.;  
553 Hidalgo, M. C.; Navío, J. A. *J. Photochem. Photobiol. A: Chem.* **2006**,  
554 *179*, 20.
- 555 (18) Colon, G.; Hidalgo, M. C.; Munuera, G.; Ferino, I.; Cutrufello,  
556 M. G.; Navio, J. A. *Appl. Catal., B* **2006**, *63*, 45.
- 557 (19) Bokhimi, X.; Morales, A.; Lopez, T.; Gomez, R.; Navarrete, J. J.  
558 *Sol-Gel Sci. Tech.* **2004**, *29*, 31. Bokhimi, X.; Morales, A.; Novaro, O.  
559 *Chem. Mater.* **1997**, *9*, 2616.
- 560 (20) Ortiz-Islas, E.; Lopez, T.; Navarrete, J.; Bokhimi, X.; Gomez, R.  
561 *J. Mol. Catal. A: Chem.* **2005**, *228*, 345.
- 562 (21) Yan, M.; Chen, F.; Zhang, J.; Anpo, M. *J. Phys. Chem. B* **2005**,  
563 *109*, 8673.
- 564 (22) Bokhimi, X.; Morales, A.; Novaro, O. *Chem. Mater.* **1997**, *9*, 2616.
- 565 (23) Periyat, P.; Pillai, S. C.; McCormack, D. E.; Colreavy, J.; Hinder,  
566 S. J. *J. Phys. Chem. C* **2008**, *112*, 7644.
- 567 (24) Sakthivel, S.; Janczarek, M.; Kisch, H. *J. Phys. Chem. B* **2004**, *108*,  
568 19384. Ho, W.; Yu, J. C.; Lee, S. *J. Solid State Chem.* **2006**, *179*, 1171.
- 569 (25) Choi, S. Y.; Mamak, M.; Coombs, N.; Chopra, N.; Ozin, G. A.  
570 *Adv. Funct. Mater.* **2004**, *14*, 335.
- (26) Pal, M.; Serrano, J. G.; Santiago, P.; Pal, U. *J. Phys. Chem. C* **2007**, *111*, 96.
- (27) Irie, H.; Watanabe, Y.; Hashimoto, K. *J. Phys. Chem. B* **2003**, *107*,  
5483. Chen, X.; Burda, C. *J. Phys. Chem. B* **2004**, *107*, 5483. Chen, X.;  
549 Lou, Y.; Samia, A. C. S.; Burda, C.; Gole, J. L. *Adv. Funct. Mater.* **2005**,  
550 *15*, 41.
- (28) Yu, J. C.; Ho, W.; Yu, J.; Yip, H.; Wong, P. K.; Zhao, J. *Environ.*  
551 *Sci. Technol.* **2005**, *39*, 1175.
- (29) Ohno, T.; Akiyoshi, M.; Umebayashi, T.; Asai, K.; Mitsui, T.;  
552 Matsumura, M. *Appl. Catal., A* **2004**, *265*, 115.
- (30) Bringer, C. J.; Scherer, G. W. *Sol-Gel Science*; Academic Press:  
553 New York, 1990.
- (31) Schubert, U. *J. Mater. Chem.* **2005**, *15*, 3701.
- (32) Gopal, M.; Chan, W. J. M.; De Jonghe, L. C. *J. Mater. Sci.* **1997**,  
554 *32*, 6001.
- (33) Xie, C.; Yang, Q.; Xu, Z.; Liu, X.; Du, Y. *J. Phys. Chem. B* **2006**,  
555 *110*, 8587. Yamabi, S.; Imai, H. *Thin Solid Films* **2003**, *434*, 86.
- (34) Samantaray, S. K.; Mohapatra, P.; Parida, K. *J. Mol. Catal. A:*  
556 *Chem.* **2003**, *198*, 277.
- (35) Rhee, C. H.; Lee, J. S.; Chung, S. H. *J. Mater. Res.* **2005**, *20*, 3011.
- (36) Wilhelm, P.; Stephan, D. *J. Photochem. Photobiol. A: Chem.* **2007**,  
557 *185*, 19.
- (37) Aronson, B. J.; Blanford, C. F.; Stein, A. *Chem. Mater.* **1997**, *9*,  
558 2842. Beyers, E.; Cool, P.; Vansant, E. F. *J. Phys. Chem. B* **2005**, *109*,  
559 10081. Busuioc, A. M.; Meynen, V.; Beyers, E.; Mertens, M.; Cool, P.;  
560 Bilba, N.; Vansant, E. F. *Appl. Catal., A* **2006**, *312*, 153.
- (38) Chen, F.; Zhao, J.; Hidaka, H. *Int. J. Photoenergy* **2003**, *5*, 209.
- (39) Ryu, J.; Choi, W. *Environ. Sci. Technol.* **2008**, *42*, 294.
- (40) Su, W.; Zhang, J.; Feng, Z.; Chen, T.; Ying, P.; Li, C. *J. Phys.*  
561 *Chem. C* **2008**, *112*, 7710.
- (41) Ramis, G.; Busca, G.; Lorenzelli, V. *J. Chem. Soc. Faraday Trans.*  
562 *I* **1987**, *83*, 1591.
- (42) Hadjivanov, K. *Appl. Surf. Sci.* **1998**, *135*, 331.
- (43) Burda, C.; Lou, Y. B.; Chen, X. B.; Samia, A. C. S.; Stout, J.;  
563 Gole, J. L. *Nano Lett.* **2003**, *3*, 1049.
- (44) Umebayashi, T.; Yamaki, T.; Tanala, S.; Asai, K. *Chem. Lett.* **2003**,  
564 *32*, 330.
- JP808444Y 608