

2007

## Silver Doped Titanium Dioxide Nanomaterials for Enhanced Visible Light Photocatalysis

Michael Seery

*Technological University Dublin, michael.seery@tudublin.ie*

Reena George

Suresh Pillai

*Technological University Dublin, suresh.pillai@tudublin.ie*

*See next page for additional authors*

Follow this and additional works at: <https://arrow.tudublin.ie/cenresart>

 Part of the [Inorganic Chemistry Commons](#)

### Recommended Citation

Seery, M.K. et al. (2007) Silver doped titanium dioxide nanomaterials for enhanced visible light photocatalysis, *Journal of Photochemistry and Photobiology A*, vol. 189, no. 2-3, 2007, 258-263. doi:10.1016/j.jphotochem.2007.02.010

This Article is brought to you for free and open access by the Crest: Centre for Research in Engineering Surface Technology at ARROW@TU Dublin. It has been accepted for inclusion in Articles by an authorized administrator of ARROW@TU Dublin. For more information, please contact [arrow.admin@tudublin.ie](mailto:arrow.admin@tudublin.ie), [aisling.coyne@tudublin.ie](mailto:aisling.coyne@tudublin.ie).



This work is licensed under a [Creative Commons Attribution-Noncommercial-Share Alike 4.0 License](#)

---

**Authors**

Michael Seery, Reena George, Suresh Pillai, and Patrick Floris



## Silver doped titanium dioxide nanomaterials for enhanced visible light photocatalysis

Michael K. Seery<sup>a,\*</sup>, Reenamole George<sup>a</sup>, Patrick Floris<sup>a</sup>, Suresh C. Pillai<sup>b</sup>

<sup>a</sup> School of Chemical and Pharmaceutical Sciences, Dublin Institute of Technology, Kevin St., Dublin 8, Ireland

<sup>b</sup> Centre for Research in Engineering Surface Technology (CREST), Dublin Institute of Technology, Camden Row, Dublin 8, Ireland

Received 4 December 2006; received in revised form 30 January 2007; accepted 14 February 2007

### Abstract

This paper presents a systematic study on two different preparation methods for titanium dioxide with silver. The silver can be incorporated by irradiating the reaction mixture during preparation to reduce silver ion to silver metal or by direct calcination of the sol-gel material to decompose silver nitrate to silver. Of the two methods, we found the latter produces a more effective photocatalytic material (6–50% improvement in catalytic efficiency), which is attributed to the fact that the silver is homogeneously dispersed throughout the material. The efficiency of the materials were examined using a Q-Sun solar simulator (visible light) and in Dublin summer sunlight (latitude 54°N). In both cases, the addition of increasing amounts of silver, for both batches of samples, significantly increases the rate of degradation of a model dye, rhodamine 6G (R6G), increasing the rate of degradation from 0.06 min<sup>-1</sup> for TiO<sub>2</sub> to 0.34 min<sup>-1</sup> for 5 mol% Ag-TiO<sub>2</sub>. This is attributed to the increasing visible absorption capacity due to the presence of silver nanoparticles.

© 2007 Published by Elsevier B.V.

**Keywords:** Titanium dioxide; Silver; Visible light; Photocatalysis

### 1. Introduction

Metal oxide photocatalytic degradation of organic pollutants has attracted significant attention by researchers because of its usefulness in tackling environmental contaminants [1,2]. Titanium dioxide is one of the most widely studied semi-conducting photocatalysts for the degradation of organic contaminants from water and air, because of its physical and chemical stability, high catalytic activity, high oxidative power, low cost and ease of production [1–4]. However, though it is a good catalyst, its wide band gap (3.2 eV) limits TiO<sub>2</sub> use of visible light as the light source. This has knock-on implications for the use of titania materials as solar or room-light activated catalysts, because the majority of sunlight consists of visible light and only a 3–5% of UV light. Hence increasing the efficiency of visible photocatalysis is important for the practical application of this technique in future. Numerous studies have been carried out to develop the

visible light activity to TiO<sub>2</sub> [5–10] and these studies include the doping with metal and non-metal ions [11–14], dye sensitisation [15], and semiconductor coupling, etc.

As well as the energy of incident light, the photocatalytic efficiency depends on the rate of recombination of photoexcited electrons and holes. The photocatalytic mechanism involves the excitation of valence electrons to the conduction band by absorbing the UV light, resulting in the formation of holes in the valence band [16]. These electrons and holes can undergo subsequent reduction and oxidation before the recombination reaction. However, the lifetimes of these species are very small and in the absence of suitable scavengers, they will dissipate the stored energy within a few nanoseconds by recombination. Many studies have been carried out to improve the photocatalytic activity by reducing the recombination reaction by the insertion of noble metals [17–19] and it is found that doping with silver has been of considerable interest because of its potential applications. The importance in medical applications of silver and antibacterial activity of TiO<sub>2</sub> together led researchers to think about the manufacture of silver doped titania coated sanitary wares [20], medical devices, food preparation surfaces, air conditioning filters, etc. Silver can trap the excited electrons from

\* Corresponding author. Tel.: +353 1 4024758; fax: +353 1 4024989.

E-mail addresses: [Michael.seery@dit.ie](mailto:Michael.seery@dit.ie) (M.K. Seery), [suresh.pillai@dit.ie](mailto:suresh.pillai@dit.ie) (S.C. Pillai).

TiO<sub>2</sub> and leave the holes for the degradation reaction of organic species [21,22]. It also results in the extension of their wavelength response towards the visible region [23–25]. Moreover, silver particles can facilitate the electron excitation by creating a local electric field [26], and plasmon resonance effect in metallic silver particles shows a reasonable enhancement in this electric field [15]. The effect of Ag doping on titania and its photocatalytic activity by UV irradiation was studied by Chao et al. [11] (by the sol–gel method) and they found that Ag doping promotes the anatase to rutile transformation, which is attributed to the increase in specific surface area which causes the improvement in photocatalytic activity, and enhances the electron–hole pair separation.

There are some contradictory results also reported showing the decreased activity of silver modified titania [28,29]. This may be due to their preparation method, nature of organic molecules, photoreaction medium, or the metal content and its dispersion. Even though there are many studies showing the photocatalytic activity of silver doped titania [11,31–33] the exact mechanism and the role of silver is under debate.

In this paper we report a systematic comparative study of solar initiated photocatalytic activity of sol–gel titania with silver nitrate added in various amounts. The silver ion was either reduced during the synthesis phase by irradiating the sample with light (pre-irradiated) or formed during calcination of the sol–gel material via decomposition of silver nitrate (not pre-irradiated). This method allows for the formation of sol–gel derived, homogeneously silver doped stable titania. We examined the structural characteristics of this material using X-ray diffraction (XRD), electron microscopy and absorption spectra and the effect of these materials on the photodegradation of a model dye, rhodamine 6G (R6G).

## 2. Experimental

Titanium tetraisopropoxide (97%), acetic acid (99.7%) and silver nitrate (99%) were purchased from Aldrich. Rhodamine 6G was purchased from Eastman and was of analytical reagent grade and used without further purification. Deionised water was used in all experimental preparations. The samples were prepared by a modified sol–gel route [34]. Titanium isopropoxide (25 ml) was added to acetic acid (48 ml) with stirring. Then water (150 ml) was added to the mixture dropwise with vigorous stirring. (The titanium isopropoxide, acetic acid and water are in 1:10:100 molar ratios.) The solution was stirred for 8 h to get a clear transparent sol and allowed to dry at 100 °C, after which it was calcined at 600 °C in air for 2 h at a ramp rate of 5 °C/min. To prepare silver doped titania, the above procedure was repeated, including silver nitrate (1, 2, 3 and 5 mol%) when adding water to the titanium isopropoxide mixture. The sol was then either irradiated with 250 W bulb for 60 min (“pre-irradiated samples”) after which they were kept in an oven set at 100 °C until all the solvent evaporated or directly placed in the oven (“not pre-irradiated”). The dried powders were calcined at 600 °C for 2 h at a ramp rate of 5 °C/min. The photocatalytic activities of the materials were studied by examining the degradation reaction of R6G. For powder samples, about 0.06 g of titania sample

was dispersed in 50 ml of R6G solution having concentration  $5 \times 10^{-6}$  M. This suspension was irradiated with light using Q-Sun solar test chamber (0.68 W/m<sup>2</sup> at 340 nm). The suspension was stirred during irradiation, but was not purged with any gas. Degradation was monitored by collecting aliquots at increasing time intervals. The aliquots were centrifuged and absorption spectra were recorded using Perkin-Elmer Lambda 900 spectrophotometer. The terrestrial activity of the highly active silver doped sample and the standard TiO<sub>2</sub> was determined by carrying out the reaction under Dublin summer sunlight at noon. The intensity of the sunlight was determined by a Solar light Co. Broadband radiometer PMA 2107 (Philadelphia) [35] which gave approximately 12.4 W/m<sup>2</sup> summed across the 260–400 nm wave band. Band gaps of the coated materials were measured by recording the transmission spectra of spin-coated films on glass. XRD were collected using a Siemens D 500 X-ray diffractometer, with a diffraction angle range  $2\theta = 10\text{--}70^\circ$  using Cu K $\alpha$  radiation. UV–vis absorption spectra were obtained on a Perkin-Elmer Lambda 900 spectrophotometer.

The mass fraction of rutile in the calcined samples was calculated by Spurr formula (Eq. (1)) which is the relationship between integrated intensities of anatase (1 0 1) and rutile (1 1 0) peaks where  $I_A$  and  $I_R$  are the integrated peak intensities of anatase and rutile peaks, respectively.

$$X_R = \frac{1}{1 + 0.8(I_A/I_R)} \quad (1)$$

Particle size was determined by the Scherrer equation which calculates crystalline size using the expression  $(0.9\lambda/(\beta \cos \theta))$ , where  $\lambda$  is the X-ray wavelength,  $\theta$  the Bragg angle and  $\beta$  is the line broadening.

## 3. Results

### 3.1. XRD analysis

XRD of the doped and undoped titania samples irradiated with light for 40 min to reduce the silver nitrate and calcined at 600 °C are shown in Fig. 1. The materials show a high degree of crystallinity and existence of fully anatase phase at 600 °C. We chose 600 °C as calcination temperature as this temperature was found to have highest activity among samples calcined at different temperatures, due to the fact that the material is in the anatase phase and is highly crystalline [7]. However, there are no obvious peaks showing the presence of silver in the XRD of silver doped titania samples calcined at 600 °C, which indicates that the discrete silver particles are homogeneously distributed in the titania matrix. This conclusion is further verified by studying an XRD of Ag–TiO<sub>2</sub> calcined at 700 °C which shows the presence of peaks corresponding to the metallic silver at 38.2, 44.4 and 64.5. Interestingly, the presence of small amounts of silver (1, 3 mol%) result in the anatase to rutile phase transformation occurring at a higher temperature. This differs from other work where addition of silver resulted in the rutile phase forming at 500 °C. In samples calcined at 700 °C, silver peaks are detected (Supplementary information, Table 1). This is also in a good agreement with the values of peaks obtaining by calcina-

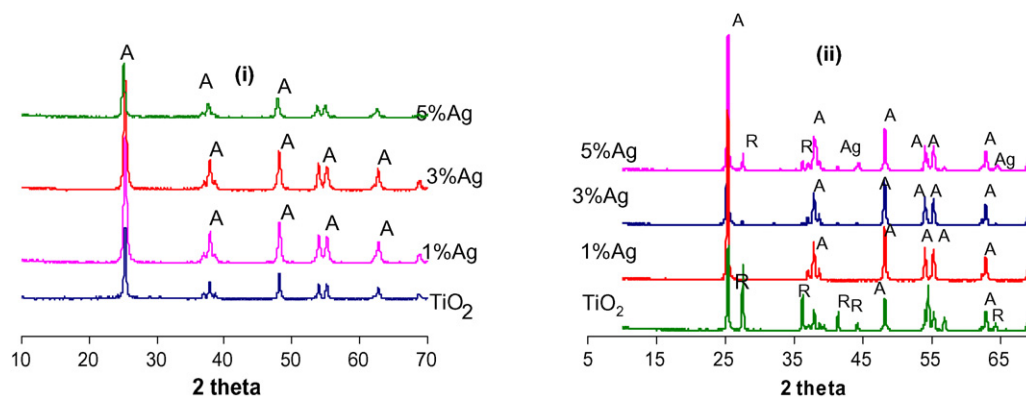


Fig. 1. XRD of: (i) undoped and silver doped titania (not pre-irradiated) all calcined at 600 °C, and (ii) undoped 1, 3, and 5 mol% and Ag doped titania all calcined at 700 °C (peak values listed in Supplementary information, Table 1).

tion of silver nitrate alone (Supplementary information, Fig. 1a). The 700 °C sample indicates that at this higher temperature, the silver particles homogeneously distributed throughout the TiO<sub>2</sub> matrix begin to diffuse towards the edges of the material forming agglomerates. There was no measurable difference in the XRD spectra due to pre-irradiation of samples (Fig. 2).

In order to study the effect of silver on particle size, crystallite sizes as measured from the XRD spectra (Supplementary information, Table 2). It has been found that the particle size reduces as a result of Ag addition. However, there is no significant reduction in particle size observed with increasing silver amounts after this initial reduction.

### 3.2. Visible light absorption capability

Diffuse reflectance spectroscopy (DRS) were used to record absorbance capacity of the powders. As a general trend, increasing amounts of Ag results in a higher visible absorbance capability of the materials. This is as expected, as previous workers who included silver in the titania matrix observed similar results. For example, Mills et al. used surface enhanced resonance Raman spectroscopy to investigate silver doped titania films, and observed an increased absorption in the visible region [36]. In addition, in our own laboratories we are currently

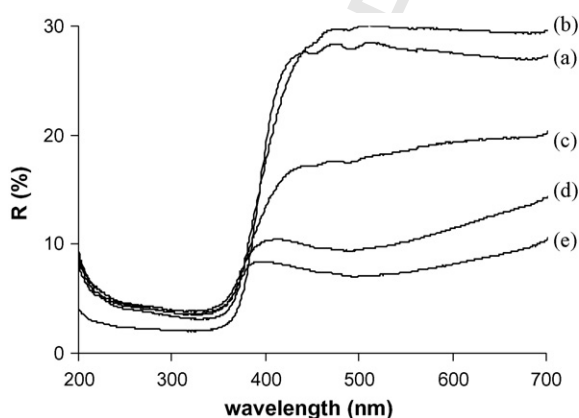


Fig. 2. Diffuse reflectance spectra of: (a) undoped, (b) 1 mol%, (c) 2 mol%, (d) 3 mol% and (e) 5 mol% (not pre-irradiated) silver doped titania.

investigating thin films of these materials and the transmission spectra show the presence of a band at ~400 nm, which is due to the presence of silver metal. It is noted that upon illumination of TiO<sub>2</sub>/AgNO<sub>3</sub> solution during the preparation time stable colloidal solutions were obtained which displays the progressive evolution of characteristic silver surface plasmon band at 400 nm. This is indicative of the formation of nanometer sized silver metal, corresponding to a size of approximately 20 nm [37]. These silver metals can easily disperse into the TiO<sub>2</sub> lattice. At this plasmon band resonance frequency, there would be efficient visible light absorption.

### 3.3. Photocatalytic studies

In order to examine the photocatalytic activity of the materials prepared we studied the effect of photodegradation of R6G in the presence of the undoped and doped materials. Silver metal can be incorporated by photoreduction of Ag<sup>+</sup> [38] or by allowing the silver salt to decompose during calcination [39]. In order to examine the effect of pre-irradiation, we prepared two parallel sets of doped materials by the sol–gel method—the first where the silver nitrate was added and the solution irradiated for 60 min before drying and calcination (“pre-irradiated”), the second where the silver nitrate was added and the material dried and calcined without irradiation (“not pre-irradiated”). The results of this study are shown in Table 1. R6G showed minimal degradation in the absence of a catalyst over the same time period.

Table 1

The rate constant for degradation of R6G for samples with different mol percentages of silver—after either pre-experimental irradiation to reduce AgNO<sub>3</sub> or sample which were directly calcinated

Ag (mol%)	Rate constant (min <sup>-1</sup> )	
	No pre-irradiation	Pre-irradiation (60 min)
0	0.06	–
1	0.16 ± 0.02	0.10 ± 0.01
2	0.18 ± 0.02	0.17 ± 0.02
3	0.24 ± 0.02	0.21 ± 0.03
5	0.34 ± 0.03	0.24 ± 0.03

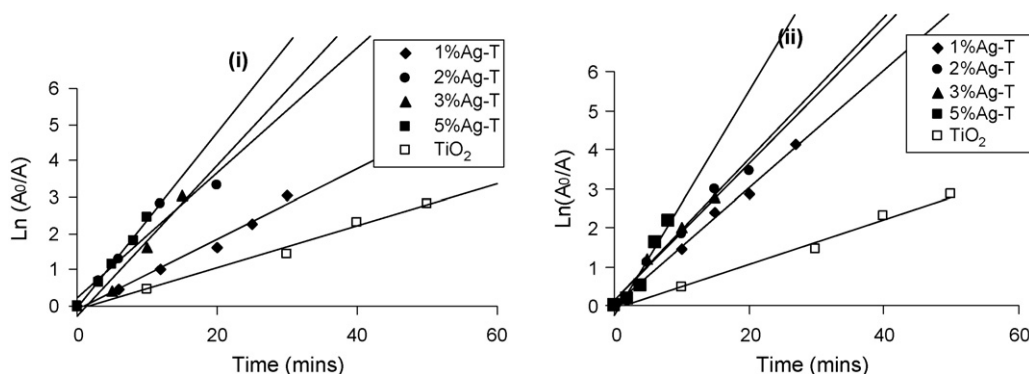


Fig. 3. Kinetic analysis showing the effect of increasing concentration of Ag on the rate of degradation of R6G where the preparation method involved: (i) no pre-irradiation and (ii) with pre-irradiation.

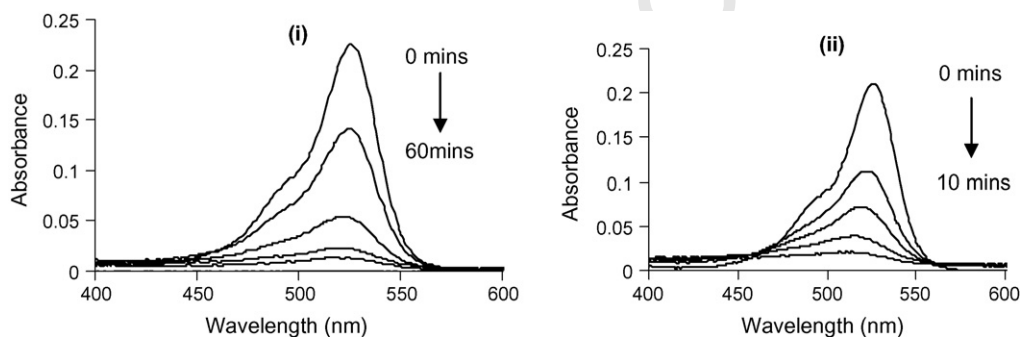


Fig. 4. Absorption spectra of the degradation of R6G in presence of: (i)  $\text{TiO}_2$  and (ii) 5 mol% Ag doped  $\text{TiO}_2$ .

214 For both pre-irradiated and non-irradiated samples, the activ-  
215 ity of the catalyst is enhanced significantly on addition of silver,  
216 with the degradation rate increasing from  $0.06$  to  $0.24 \text{ min}^{-1}$   
217 for the pre-irradiated samples and to  $0.34 \text{ min}^{-1}$  for the non-  
218 pre-irradiated samples, corresponding to half lives of 12.0, 2.8  
219 and 2.4 min, respectively (Fig. 3).

220 When comparing the effects of pre-irradiation, the samples  
221 that were not pre-irradiated were consistently higher than those  
222 which were not pre-irradiated, although the enhancement was  
223 not marked. Sample absorption spectra for these experiments  
224 are shown in Fig. 4. A significant blue shift in the absorption  
225 maximum is observed in all silver modified materials (typically  
226 10–12 nm), but no real shift is observed for titania.

227 Fig. 5 shows the rate constant of degradation as a function  
228 of mol% of silver. As observed in the transmission and DRS

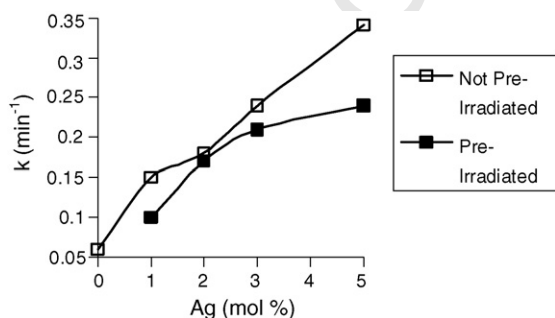


Fig. 5. Plot of rate constants of degradation against mol% of Ag with pre-irradiated and non-pre-irradiated samples.

229 spectra, increasing amounts of silver doping result in increased  
230 visible light absorption and hence enhanced photocatalytic activ-  
231 ity. We examined the rate of degradation of 10 mol% Ag– $\text{TiO}_2$   
232 (not pre-irradiated). A degradation rate constant of  $0.07 \text{ min}^{-1}$   
233 was observed.

234 According to our study, it is clear that with the increase in  
235 the time of pre-irradiation, the amount of photo reduced Ag  
236 increases and which causes the growth of silver clusters and  
237 thereby decreasing the active sites for the photocatalytic reac-  
238 tion. This is confirmed by varying the pre-irradiation time of  
239 the 5% Ag– $\text{TiO}_2$  sample, which shows the rate of degradation  
240 decrease from no pre-irradiation ( $0.34 \text{ min}^{-1}$ ) through 20 min  
241 ( $0.28 \text{ min}^{-1}$ ), 40 min ( $0.27 \text{ min}^{-1}$ ) and 60 min pre-irradiation  
242 ( $0.24 \text{ min}^{-1}$ ).

243 The degradation of rhodamine 6G was examined in the  
244 presence of silver nanoparticles and in the absence of titania.  
245 Minimal degradation was observed over 6 h irradiation in the  
246 Q-Sun chamber, indicating the requirement of the presence of  
247 titania for the photocatalytic mechanism.

### 3.4. Sunlight as a light source

248 The above experiments were conducted in a Q-Sun solar  
249 chamber which models the solar spectrum, at a power corre-  
250 sponding to noon time, summer day, in Florida. We wanted to  
251 examine the ability of the materials at lower intensities. This  
252 was achieved by varying the Q-Sun irradiance intensity ( $0.68$ ,  
253  $0.6$ ,  $0.5$ ,  $0.4 \text{ W/m}^2$ ) which resulted in a decrease in the effi-  
254 ciency of the materials (Supplementary information, Table 3).  
255

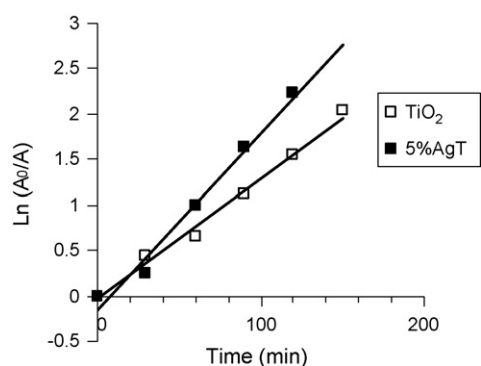


Fig. 6. Comparison of TiO<sub>2</sub> and 5% Ag–TiO<sub>2</sub> kinetics of degradation of R6G with sunlight as a light source.

More importantly however, experiments were conducted with solutions of R6G in the presence of titania and silver doped titania (5%) placed in a sunny window behind plate glass (cut-off 350 nm). The kinetic analysis showing the rate of reaction with undoped titania and 5 mol% Ag doped titania (pre-irradiated) is given in Fig. 6. In this case, rate constants for decomposition are  $1.95 \times 10^{-2}$  and  $1.3 \times 10^{-2} \text{ min}^{-1}$  for doped and undoped titania, respectively, corresponding to half lives of 52 and 35 min. These studies show our materials to be active in maritime climates such as Ireland.

## 4. Discussion

### 4.1. Characterisation of materials

The preparation method used to synthesise titania and silver doped titania involves the use of acetic acid and titanium isopropoxide. This method has advantages over other methods in that the anatase to rutile transformation temperature is held off until approximately 700 °C [34]. Other studies in this area have reported that the anatase to rutile transformation for silver doped titania can occur at lower temperatures with increment in doping level of silver [11]. As anatase is a more photoactive form of titania, this method allows us prepare high temperature stable silver doped anatase material. XRD analysis was also performed to determine the effect of silver doping in the phase transformation at higher temperature. The titania samples prepared by this modified sol–gel method contains 48.7% rutile at 700 °C where as 5 mol% silver doped sample at 700 °C contains only 13.2% rutile. Furthermore, the 1 and 3% Ag doped titania still exist in the anatase phase at 700 °C. Hence with the suitable amount of silver, the anatase to rutile transformation is pushed to an even higher temperature. This method provides for homogeneously distributed silver in samples calcined at 600 °C, as the presence of silver metal is only detectable in the 5% Ag–TiO<sub>2</sub> sample calcined at 700 °C. This is also because, the Ag–O bonding is much weaker than Ti–O and Ag–Ag bonding and Ag atom possesses higher surface free energy than the TiO<sub>2</sub> [39]. Hence during calcination the Ag atoms have a tendency to aggregate into metallic Ag clusters. This is further examined by carrying out an experiment using 50:50 TiO<sub>2</sub>:Ag mixture, calcined at 600 °C. XRD (Supplementary information, Fig. 1b) showed the presence of

silver and titania peaks. It is interesting to notice that there were no silver oxide peaks or any other phases such as silver titanate present.

### 4.2. Synthetic procedure and effect on photocatalytic activity

We compared two methods for introducing metallic silver into the TiO<sub>2</sub> material. The first was to directly reduce the AgNO<sub>3</sub> material to Ag<sup>0</sup> by irradiating the samples with light for a fixed time. The second was to directly calcinate the sample and allow the thermal decomposition of silver nitrate to occur according to the scheme:



The directly calcinated samples (i.e. non-pre-irradiated) show slightly better photocatalytic activity. It is known that silver particles deposited on the surface of the titania can act as electron–hole separation centres [40]. The radius of Ag<sup>+</sup> ions (126 pm) is much larger than that of Ti<sup>4+</sup> (68 pm) and so the Ag<sup>+</sup> ions introduced by the sol–gel process would not enter into the lattice of anatase phase. During calcination, these uniformly dispersed Ag<sup>+</sup> ions would gradually migrate from the volume of the TiO<sub>2</sub> to the surface by enhancing their crystallinity, resulting in silver deposited on the surface on calcination [41]. Electron transfer from conduction band of TiO<sub>2</sub> to the metallic silver particles at the interface is possible, because the Fermi level of TiO<sub>2</sub> is higher than that of silver metal [42]. This results in the formation of Schottky barrier at the Ag–TiO<sub>2</sub> contact region, which improves the photocatalytic activity. In addition, there may be residual Ag<sup>+</sup> ions within the material, acting as efficient electron traps may contribute to the enhanced photocatalytic activity of these samples over the pre-irradiated samples. For the pre-irradiated samples, we propose that the main reason for reduced efficiency as compared to directly calcinated samples is that in the case of titania, photoreduced Ag *cannot* be highly dispersed in the surface of TiO<sub>2</sub>, so that the amount of active sites on the Ag–TiO<sub>2</sub> surface cannot markedly increase and thereby electronic structure of TiO<sub>2</sub> cannot be changed significantly [44]. The leveling off in photocatalytic activity on further increasing amount of silver is most likely due to the fact that as the concentration of silver becomes large, it results in one of a number of effects: (i) it acts as a barrier preventing light absorption by titania, (ii) it prevents the organic substrate from contacting the titania surface and (iii) the silver may become a significant centre for electron–hole recombination [44].

It has been reported that the photodegradation of rhodamine results from both the de-ethylation and degradation of rhodamine chromophore [45]. De-ethylation is occurring on the surface and rhodamine degradation is mainly a bulk solution process. According to Amal and co-workers [46,47] the enhancing effect of silver deposits on TiO<sub>2</sub> mainly depends on the molecular structure of substrate to be oxidised. The more C=O or C–O bond that a molecule possess the more probable the enhancement of degradation in presence of silver. In addition, de-ethylation (a surface bound process) is characterised by a blue shift in the absorption spectrum of rhodamine on degradation [32]. In our

349 samples, the silver doped titania all show significant blue shifts,  
350 whereas the titania shows little shift. This leads to the conclu-  
351 sion that the silver samples achieve higher surface adsorption,  
352 and hence result in better photodegradation.

353 These materials are visible light active. There are two parallel  
354 mechanisms which may result in electron population of the con-  
355 duction band of the material—(i) that the rhodamine 6G absorbs  
356 visible light and injects an electron into the conduction band of  
357 the titania material, and (ii) that the material itself absorbs visi-  
358 ble light, probably facilitated by the surface plasmon absorption  
359 of the silver doped materials. It is probable that the two mech-  
360 anisms are happening in parallel, indeed some commentators  
361 have questioned the suitability of dyes such as methylene blue  
362 for photocatalytic studies [48]. However, as important as the  
363 materials ability to absorb visible light is its ability to retain  
364 charge separation, and limit recombination. In comparing our  
365 materials, we are comparing not only visible light activation, but  
366 also efficiency of the materials to subsequently form hydroxyl  
367 radicals. Therefore, photosensitisation, if it is occurring, would  
368 enhance both titania samples and silver modified samples. The  
369 role of silver is clearly limiting the recombination rate and sub-  
370 sequently allowing a greater proportion of hydroxyl radicals to  
371 form.

## 372 5. Conclusions

373 This paper describes the synthesis of TiO<sub>2</sub> containing differ-  
374 ent amounts of silver metal by the sol–gel route. The synthetic  
375 method where the silver nitrate was not reduced by light before  
376 calcination resulted in a slightly more efficient photocatalysis  
377 over that which did. All materials with added silver showed visi-  
378 ble light activation in both the Q–Sun solar simulator and Dublin  
379 sunlight, with the activity increasing with increasing amounts of  
380 silver.

## 381 Uncited references

382 [27,30,43].

## 383 Acknowledgement

384 RG would like to thank the Postgraduate R&D Skills Pro-  
385 gramme (Strand 1) for funding for this work.

## 386 Appendix A. Supplementary data

387 Supplementary data associated with this article can be found,  
388 in the online version, at doi:10.1016/j.jphotochem.2007.02.010.

## 389 References

- 390 [1] A. Fujishima, T.N. Rao, D.A. Tryk, *J. Photochem. Photobiol. C* 1 (2000)  
391 1.  
392 [2] M.R. Hoffmann, S.T. Martin, W. Choi, D.W. Bahnemann, *Chem. Rev.* 95  
393 (1995) 69.  
394 [3] A. Fujishima, K. Honda, *Nature* 238 (1972) 37.  
395 [4] T. Hisanga, K. Harada, K. Tanaka, *J. Photochem. Photobiol. A* 54 (1990)  
113.

- [5] K.N.P. Kumar, K. Keizer, A.J. Burggraaf, T. Okubo, *Nature* 358 (1992) 48. 396  
[6] C. Wang, J. Ying, *Chem. Mater.* 11 (1999) 3113. 397  
[7] S.C. Pillai, P. Periyat, R. George, D.E. McCormack, M.K. Seery, H. Hay- 398  
den, J. Colreavy, D. Corr, S.J. Hinder, *J. Phys. Chem. C* 111 (4) (2007) 399  
1605–1611. 400  
[8] Y.C. Yeh, T.T. Tseng, D.A. Chang, *J. Am. Ceram. Soc.* 72 (1989) 1472. 401  
[9] P.S. Awati, S.V. Awate, P.P. Shah, V. Ramaswamy, *Catal. Commun.* 4 (2003) 402  
393. 403  
[10] Y.H. Hsien, C.F. Chang, Y.H. Chen, S. Chen, *Appl. Catal. B* 31 (2001) 404  
241. 405  
[11] H.E. Chao, Y.U. Yun, H.U. Xiangfang, A. Larbot, *J. Eur. Ceram. Soc.* 23 406  
(2003) 1457. 407  
[12] D. Chatterjee, S. Dasgupta, *J. Photochem. Photobiol. C* 6 (2005) 186. 408  
[13] Y. Ichihashi, H. Yamashita, M. Anpo, *Funct. Mater.* 16 (1996) 12. 409  
[14] E. Hendry, F. Wang, J. Shan, T.F. Heins, M. Bonn, *Phys. Rev. B* 69 (2004) 410  
81. 411  
[15] G. Zhao, H. Kozuka, T. Yoko, *Thin Solid Films* 277 (1996) 147. 412  
[16] S. Banerjee, J. Gopal, P. Muraleedharan, A.K. Tyagi, B. Raj, *Curr. Sci.* 90 413  
(2006) 10. 414  
[17] W. Choi, A. Termin, M.R. Hoffmann, *J. Phys. Chem.* 98 (1994) 13669. 415  
[18] P.D. Cozzoli, R. Comparelli, E. Fanizza, M.L. Curri, A. Agostiano, D. 416  
Laub, *J. Am. Chem. Soc.* 126 (2004) 3868. 417  
[19] K.S. Mayya, D.I. Gittins, F. Caruso, *Chem. Mater.* 13 (2001) 3833. 418  
[20] M. Machida, K. Norimoto, T. Kimura, *J. Am. Ceram. Soc.* 88 (2005) 95Y. 419  
[21] I. Ilisz, A. Dombi, *Appl. Catal. A* 180 (1999) 35. 420  
[22] E. Stathatos, T. Petrova, P. Lianos, *Langmuir* 17 (2001) 5025. 421  
[23] P.V. Kamat, *J. Phys. Chem. B* 106 (2002) 7729. 422  
[24] M. Jacob, H. Levanon, P.V. Kamat, *Nanoletters* 3 (2003) 353. 423  
[25] E. Bae, W. Choi, *Environ. Sci. Technol.* 37 (2003) 147. 424  
[26] J.M. Hermann, H. Tahiri, Y. Ait-Ichou, G. Lossaletta, A.R. Gonzalez-Elipe, 425  
A. Fernandez, *Appl. Catal. B* 13 (1997) 219. 426  
[27] D. Bahnemann, *Solar Energy* 77 (2004) 445. 427  
[28] A. World, *Chem. Mater.* 5 (1993) 280. 428  
[29] V. Vamathevan, R. Amal, D. Beydoun, G. Low, S. McEvoy, *J. Photochem.* 429  
*Photobiol. A* 148 (2002) 233. 430  
[30] P. Falaras, I.M. Arabatzi, T. Stergioulos, M.C. Bernard, *Int. J. Photoenergy* 431  
5 (2003) 123. 432  
[31] M. Sokmen, D.W. Allen, F. Akkas, N. Kartel, F. Acar, *Water, Air Soil* 433  
*Pollut.* 132 (2001) 153. 434  
[32] H.M. Sung-suh, J.R. Choi, H.J. Hah, S.M. Koo, Y.C. Bae, *J. Photochem.* 435  
*Photobiol. A* 163 (2004) 37. 436  
[33] L. Zhang, J.C. Yu, H.Y. Yip, Q. Li, K.W. Kwong, A. Xu, P.K. Wong, 437  
*Langmuir* 19 (2003) 10372. 438  
[34] C. Suresh, V. Biju, P. Mukundan, K.G.K. Warriar, *Polyhedron* 17 (1998) 439  
3131. 440  
[35] <http://www.solarlight.com/products/PMA2107.html> (accessed November 441  
2006). 442  
[36] A. Mills, G. Hill, M. Stewart, D. Graham, W.E. Smith, S. Hodgen, P.J. 443  
Halfpenny, K. Faulds, P. Robertson, *Appl. Spectrosc.* 58 (2004) 922. 444  
[37] Y. Wang, N. Herron, *J. Phys. Chem.* 95 (1991) 525. 445  
[38] C. Hu, Y.Q. Lan, J.H. Qu, X.X. Hu, A.M.D. Wang, *J. Phys. Chem. B* 110 446  
(2006) 4066. 447  
[39] A. Chen, M.C. Bartelt, S.M. Seutter, K.F. McCarty, *Surf. Sci.* 464 (2000) 448  
L708. 449  
[40] A. Henglein, *J. Phys. Chem.* 83 (1979) 2209. 450  
[41] W.D. Kingery, H.K. Bowen, D.R. Uhlmann, *Introduction to Ceramics,* 451  
second ed., Wiley, New York, 1976, p. 457. 452  
[42] A. Sclafani, J.M. Hermann, *J. Photochem. Photobiol. A* 113 (1998) 181. 453  
[43] V. Iliiev, D. Tomova, L. Bilyarska, A. Eliyas, L. Petrov, *Appl. Catal. B* 63 454  
(2006) 266. 455  
[44] B. Xin, L. Jing, Z. Ren, B. Wang, H. Fu, *J. Phys. Chem. B* 109 (2005) 2805. 456  
[45] T. Watanabe, T. Takizawa, K. Honda, *J. Phys. Chem.* 81 (1977) 1845. 457  
[46] H. Tran, K. Chiang, J. Scott, R. Amal, *Photochem. Photobiol. Sci.* 4 (2005) 458  
565. 459  
[47] H. Tran, J. Scott, K. Chiang, R. Amal, *J. Photochem. Photobiol. A* 183 460  
(2006) 41. 461  
[48] X. Yan, T. Ohno, K. Nishijima, R. Abe, B. Ohtani, *Chem. Phys. Lett.* 429 462  
(2006) 606. 463